

# Multiple phase transitions in $\text{Ce}(\text{Rh},\text{Ir},\text{Co})\text{In}_5$ heavy-fermion superconductors

P.G. Pagliuso, R. Movshovich, A.D. Bianchi, M. Nicklas, N.O. Moreno, J.D. Thompson,  
M.F. Hundley, J.L. Sarrao and Z. Fisk

*Condensed Matter and Thermal Physics Group, MS K764, Los Alamos National Laboratory, Los  
Alamos, New Mexico 87545, U.S.A.*

## Abstract

Magnetic susceptibility, electrical resistivity and heat capacity data for single crystals of  $\text{Ce}(\text{Rh},\text{Ir})_{1-x}(\text{Co},\text{Ir})_x\text{In}_5$  ( $0 \leq x \leq 1$ ) have allowed us to construct a detailed phase diagram for this new family of heavy-fermion superconductors(HFS).  $\text{CeRh}_{1-x}\text{Ir}_x\text{In}_5$  displays superconductivity(SC) ( $T_c \lesssim 1$  K) over a wide range of composition, which develops out of and coexists ( $0.30 \lesssim x \lesssim 0.5$ ) with a magnetically ordered state, with  $T_N \sim 4$  K. For  $\text{CeCo}_{1-x}\text{Rh}_x\text{In}_5$ , the superconducting state ( $T_c \sim 2.3$  K for  $x = 0$ ) becomes a magnetic state ( $T_N \sim 4$  K, for  $x = 1$ ) with two phase transitions observed for  $0.40 \lesssim x \lesssim 0.25$ .  $\text{CeCo}_{1-x}\text{Ir}_x\text{In}_5$  also shows two transitions for  $0.30 \lesssim x \lesssim 0.75$ . For those alloys in which SC is found, a roughly linear relationship between  $T_c$  and the lattice parameter ratio  $c/a$ , was found, with composition as the implicit parameter. The interplay between magnetism and SC for  $\text{CeRh}_{1-x}(\text{Ir},\text{Co})_x\text{In}_5$  and the possibility of two distinct superconducting states in  $\text{CeCo}_{1-x}\text{Ir}_x\text{In}_5$  are discussed.

74.70.Tx, 71.27.+a, 75.40.Cx

Typeset using REVTeX

Recently, a new series of  $\text{CeMIn}_5$  tetragonal compounds for  $\text{M}=\text{Co}$ ,  $\text{Rh}$  or  $\text{Ir}$  have become the focus of much research due to the discovery of heavy-fermion superconductivity in these materials. [1–3] In particular,  $\text{CeCoIn}_5$  ( $\gamma \approx 300 \text{ mJ/mole-K}^2$ ) has the highest  $T_C = 2.3 \text{ K}$  yet observed for HFS at ambient pressure, and the SC has been claimed as unconventional and presumably magnetically mediated. [4]  $\text{CeIrIn}_5$  ( $\gamma \approx 720 \text{ mJ/mole-K}^2$ ) also shows ambient-pressure heavy-fermion SC at  $T_c \approx 0.4 \text{ K}$ . In contrast,  $\text{CeRhIn}_5$  is an antiferromagnet at ambient pressure ( $T_N \approx 3.8 \text{ K}$  and  $\gamma \approx 400 \text{ mJ/mol-K}^2$ ) [1] which evolves to a superconducting state for  $P > P_c \approx 16 \text{ kbar}$  and  $T_c \approx 2 \text{ K}$ . As such, the  $\text{CeMIn}_5$  family is a great opportunity to investigate the tunability of HF ground states using external control parameters such as pressure or doping. In this regard, recent studies of  $\text{CeRh}_{1-x}\text{Ir}_x\text{In}_5$  have revealed a remarkably rich phase diagram which is reminiscent of the high- $T_c$  cuprates. [5] The main findings of these studies were: i) SC was observed in a very wide doping range ( $0.30 < x \leq 1.0$ ), ii) Magnetism ( $T_N \approx 3.8 \text{ K}$ ) and SC ( $T_c \lesssim 1 \text{ K}$ ) *coexist* for a significant range of concentration ( $0.3 < x < 0.65$ ), and iii) The maximum  $T_c$  was found at the boundary between magnetism and SC. Here we report the generalization of Ref. 5 to include pseudo binary phase diagrams for the  $\text{Rh-Co}$  and  $\text{Ir-Co}$  alloys. Our two main results are: 1) the presence of multiple coexisting phases is a general feature of the ground states of  $\text{CeMIn}_5$  and 2) for those materials that superconduct, a universal relationship between  $T_c$  and  $c/a$ , independent of alloy composition, is found.

Figure 1 shows the generalized temperature-composition phase diagram for  $\text{Ce}(\text{Rh},\text{Ir},\text{Co})\text{In}_5$ , derived mainly from heat capacity measurements on single crystals. SC is found in wide ranges of  $x$  for  $\text{Rh-Ir}$ ,  $\text{Rh-Co}$  and  $\text{Co-Ir}$  alloys. The robustness of the superconducting state as a function of doping for these compounds is unusual for HFS. As discussed in Ref.5, details of the  $\text{Rh-Ir}$  section of this phase diagram resemble that of the high- $T_c$  cuprates. [5] Because  $\text{CeRhIn}_5$  is an antiferromagnet, and  $\text{CeIrIn}_5$  and  $\text{CeCoIn}_5$  are superconductors at ambient pressure, studies of  $\text{CeRh}_{1-x}(\text{Ir},\text{Co})_x\text{In}_5$  allow the interplay between magnetism and SC to be studied in detail. As  $\text{Co}$ ,  $\text{Rh}$ , and  $\text{Ir}$  are all isovalent, the parameter being tuned is not effective doping, but rather effective magnetic coupling or hybridization.

For both Ir and Co substitutions, a comparable and large amount of doping is required to suppress long range magnetic order. Further, both Rh-Ir and Rh-Co alloys show ranges of concentration ( $0.3 < x < 0.65$  and  $0.30 \lesssim x \lesssim 0.75$ , respectively) where two phase transition are observed by heat capacity measurements. Additional resistivity and  $\chi_{ac}$  measurements allowed us to identify the higher temperature transition as a magnetic transition and the lower-T transition as SC, consistent with the systematic evolution of ground states of the end member compounds(see Fig.1).

With respect to their proximity to magnetism, Ce-based HFS belong to a class in which ordered magnetism seems to compete with SC and in which both states have been observed concomitantly only for small windows of parameter space. [6] The phase diagram reported here is a counterexample to the above categorization because significant ranges of coexistence of these states have been found, and in fact, is more reminiscent of phase diagrams associated with U-based HFS. [6] For  $\text{CeRh}_{1-x}\text{Ir}_x\text{In}_5$  NQR,  $\mu\text{SR}$  and neutrons scattering experiments indicate *microscopic* coexistence of magnetism and SC and the absence of gross phase segregation. [7] Finally, the phase diagram of Fig.1 presents an interesting asymmetry with respect to the interaction between magnetism and SC: in the case of Rh-Ir,  $T_c$  increases as the magnetic boundary is approached, whereas in the Rh-Co case,  $T_c$  decreases. Thus, whether the SC in  $\text{CeMIn}_5$  requires proximity to magnetism to exist or is destroyed only by a sufficiently strong magnetic state remains to be seen.

Turning now to  $\text{CeCo}_{1-x}\text{Ir}_x\text{In}_5$ , two heat capacity anomalies are observed for  $0.30 \lesssim x \lesssim 0.60$ . Zero resistivity is achieved at the high-T transition and maintained through the low-T transition. Preliminary  $\chi_{ac}$  data reveal the onset of diamagnetism at the upper transition and no obvious signature at the lower one. Although powder diffraction patterns and low residual resistivity suggest otherwise, at this point we cannot rule out the possibility of sample inhomogeneity (such as a distribution of doping concentration) as being the origin of the two transition. The fact the both pure compounds  $\text{CeCoIn}_5$  and  $\text{CeIrIn}_5$  are superconductors might suggest the presence of two superconducting phase transitions.

Finally, aside from the absence of SC for compounds near  $\text{CeRhIn}_5$ , one can find a

quasi-linear increase of  $T_c$  as a function of  $x$  for  $\text{CeRh}_{1-x}(\text{Ir,Co})_x\text{In}_5$  (dashed line in Fig.1). Not coincidentally, the lattice parameter ratio  $c/a$  also increases in the sequence  $\text{CeIrIn}_5$ - $\text{CeRhIn}_5$ - $\text{CeCoIn}_5$ . Figure 2 presents  $T_c$  versus  $c/a$  for  $\text{Ce}(\text{Rh,Ir,Co})\text{In}_5$  for those compounds in which SC is observed. A linear dependence that spans more than a factor of five in  $T_c$  is apparent. Estimates of anisotropic compressibility derived from thermal expansion measurements on  $\text{CeIrIn}_5$  [8] allow the inclusion of  $T_c$  for  $\text{CeRhIn}_5$  and  $\text{CeIrIn}_5$  under pressure in the Fig.2. This surprising positive linear relationship between  $T_c$  and  $c/a$  perhaps gives support for recent calculations for magnetically mediated superconductors. [9] In these calculations, quasi-2D crystal structures and nearly commensurate antiferromagnetic correlations are essential for producing higher  $T_c$ s. Thus, the increasing of  $c/a$  in this family of compounds may increase the 2D character of the relevant spins fluctuations. However, how relatively small changes in  $c/a$  can lead to a rather dramatic tuning of the ground-state properties of these materials remains to be clarified (e.g., tuning the f-ligand hybridization, changing the symmetry of Ce crystal-field ground state, etc.) A linear fit to data on Fig.2 yields a slope  $\Delta T_c / \Delta c/a \approx 70$  K. Optimistically (and naively), a member of the  $\text{CeMIn}_5$  family with a  $c/a \approx 6$  would be a room temperature superconductor.

## REFERENCES

- [1] H. Hegger, et al. Phys. Rev. Lett. 84, 4986(2000).
- [2] C. Petrovic, et al. Europhys. Lett. 53 354-359 (2001).
- [3] C. Petrovic, et al. J. Phys.: Condens. Matter 13 L337 (2001).
- [4] R. Movshovich et al. Phys. Rev. Lett. 86, 5152 (2001).
- [5] P.G. Pagliuso, et al. to appear in Phys. Rev. B Rapid. Comm.(2001).
- [6] R.H. Heffner and M.R. Norman, Comm. Condens. Matter Phys. 17, 361 (1996).
- [7] N.J. Curro et al.; R.H. Heffner et al; W. Bao et al. unpublished.
- [8] P. Gegenwart et. al. unpublished.
- [9] P. Monthoux and G.G. Lonzarich, Phys. Rev. B, 59, 14598 (1999).

# FIGURES

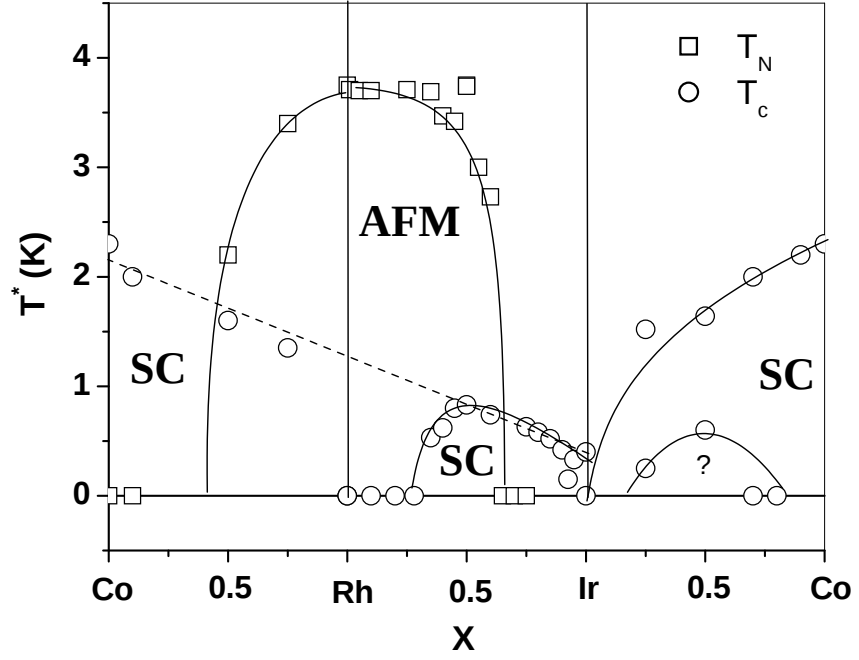


FIG. 1. Phase Diagram of  $\text{Ce}(\text{Rh},\text{Ir},\text{Co})\text{In}_5$

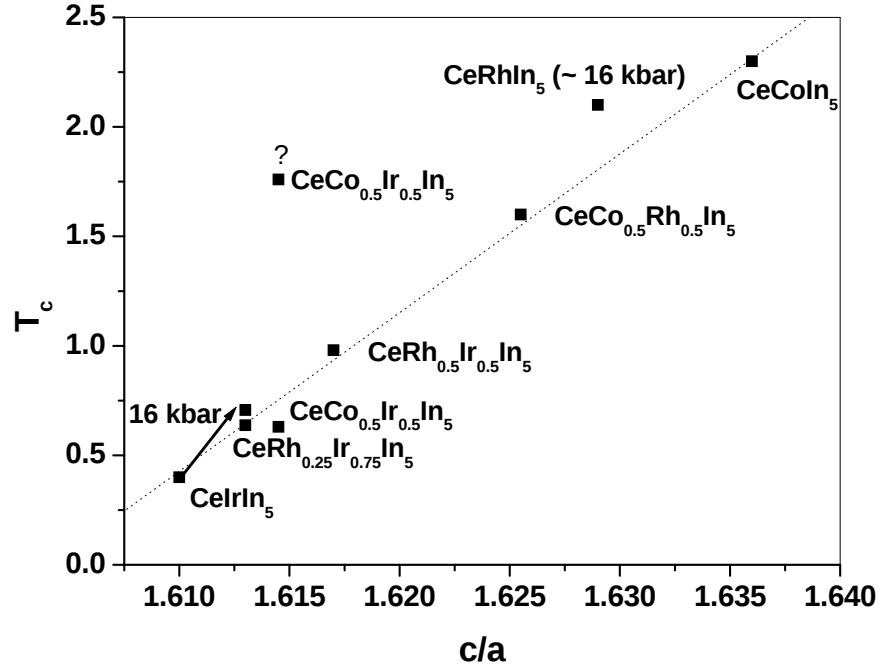


FIG. 2.  $T_C$  as a function of  $c/a$  for the  $\text{Ce}(\text{Rh},\text{Ir},\text{Co})\text{In}_5$  HFS.